

The Malaysian International Tribology Conference 2013, MITC2013

## Frictional behavior of bearing material under gas lubricated conditions

Mohd Fadzli Bin Abdollah<sup>a,b\*</sup>, Mohd Afiq Azfar Mazlan<sup>a</sup>

Hilmi Amiruddin<sup>a,b</sup>, Noreffendy Tamaldin<sup>a,b</sup>

<sup>a</sup>Faculty of Mechanical Engineering, Universiti Teknikal Malaysia Melaka, Hang Tuah Jaya, 76100 Durian Tunggal, Melaka, Malaysia

<sup>b</sup>Green Tribology and Engine Performance Research Group (G-TriboE), Universiti Teknikal Malaysia Melaka, Hang Tuah Jaya, 76100 Durian Tunggal, Melaka, Malaysia

### Abstract

In this study, a Taguchi method is employed to determine statistically the optimal design parameters, and investigate the effect of gas lubrication on friction behavior of bearing material, which is carbon chromium steel. By selecting L<sub>9</sub> Taguchi's orthogonal arrays, nine sliding tests were carried out in air, O<sub>2</sub>- and N<sub>2</sub>-gas lubrication in accordance with the ASTM standard G99-95a. The test was performed over a broad range of applied loads ( $W$ ), sliding velocities ( $v$ ) and sliding distances ( $L$ ) using a ball-on-disc tribometer. At higher applied load, sliding speed and sliding distance, it was found that gas blown to the sliding surfaces in air effectively reduced the coefficient of friction as compared to the air lubrication. In addition, based upon the mean of signal-to-noise ( $SN$ ) ratio analysis, the sliding speed is the most influencing factor for minimizing coefficient of friction. In this study, the optimal design parameters for a lower coefficient of friction ( $\mu$ ) are: lubricant = N<sub>2</sub>,  $W = 10N$ ,  $v = 1000rpm$ ,  $L = 1km$ . By using the optimal design parameters, a confirmation test successfully verified that the N<sub>2</sub>-gas lubrication reduced coefficient of friction by 24%. This is in accordance with a significant reduction of wear scar diameter and smoother worn surface on the ball.

© 2013 The Authors. Published by Elsevier Ltd.

Selection and peer-review under responsibility of The Malaysian Tribology Society (MYTRIBOS), Department of Mechanical Engineering, Universiti Malaya, 50603 Kuala Lumpur, Malaysia

*Keywords:* Gas lubrication; Carbon chromium steel; Coefficient of friction.

### Nomenclature

$F$	frictional force (N)
$W$	applied load (N)
$H$	hardness (HRC)
$R_a$	surface roughness
$SN$	signal-to-noise
$DoE$	design of experiment
$v$	sliding speed (rpm)
$L$	sliding distance (km)

\* Corresponding author. Tel.: +6-06-234-6805; fax: +6-06-234-6884

E-mail address: [mohdfadzli@utem.edu.my](mailto:mohdfadzli@utem.edu.my)

*Greek symbols*

$\mu$	coefficient of friction
$\rho$	density (g/cm <sup>3</sup> )

## 1. Introduction

Gas lubrication has several advantages, such as high precision, small friction loss, non-polluting, long life and attractive for high-temperature applications [1]. Meanwhile, gas-lubricated bearing is virtually frictionless, silent, and vibration-free. Gas bearings can be used for extremely large surface velocities. A gas bearing can eliminate the risk of contaminating a process with lubricant.

Cong et al. [2] found that HFC-134a gas significantly reduces the friction and wear of all the ceramic couples (ionic ceramics Al<sub>2</sub>O<sub>3</sub> and ZrO<sub>2</sub>, and the covalent ceramics Si<sub>3</sub>N<sub>4</sub> and SiC rubbing against an Al<sub>2</sub>O<sub>3</sub> ball), and that the ionic ceramic pairs show lower friction and wear. Oxygen has been found to lubricate SiC by the formation of silica and the release of graphite-like material [3], while benzene and acetone vapors have been found to form sticky reaction products, which reduce the friction and wear of ZrO<sub>2</sub> [4].

From the past studies, the friction of materials is effectively reduced by different gas lubrication. Thus, in this study, the friction behavior of bearing material, which is carbon-chrome steel, sliding in air with O<sub>2</sub>- or N<sub>2</sub>-gas blows are investigated using a systematic approach, which is Taguchi method. The optimal design parameters and the most significance parameter are obtained by employing analysis of signal-to-noise (*SN*) ratio.

## 2. Experimental procedures

### 2.1. Design of Experiment (DoE)

Prior to experimental work, *DoE* using Taguchi method was employed. Four design parameters were determined (lubricant, applied load, sliding speed and sliding distance) and three levels were taken for each parameter, as shown in Table 1. In this study, the L<sub>9</sub> (3<sup>4</sup>) orthogonal arrays was selected using Minitab statistical software, as shown in Table 2.

Table 1. Design parameters at three different levels

Level	Design parameters			
	Lubricant	Applied load ( <i>W</i> ), N	Sliding speed ( <i>v</i> ), rpm	Sliding distance ( <i>L</i> ), km
1	Air	5	50	1
2	N <sub>2</sub> -gas	10	1000	3
3	O <sub>2</sub> -gas	20	1500	5

Table 2. Taguchi L<sub>9</sub> (3<sup>4</sup>) orthogonal arrays

Test	Design parameters			
	Lubricant	Applied load ( <i>W</i> ), N	Sliding speed ( <i>v</i> ), rpm	Sliding distance ( <i>L</i> ), km
1	Air	5	500	1
2	Air	10	1000	3
3	Air	20	1500	5
4	N <sub>2</sub> -gas	5	500	5
5	N <sub>2</sub> -gas	10	1000	1
6	N <sub>2</sub> -gas	20	1500	3
7	O <sub>2</sub> -gas	5	500	3
8	O <sub>2</sub> -gas	10	1000	5
9	O <sub>2</sub> -gas	20	1500	1

## 2.2. Materials

The materials used in this study were carbon-chrome steel (SKF bearing) for a ball and EN-31 for a disc. The ball has an average surface roughness (*R<sub>a</sub>*) of 0.023μm. The mechanical properties of materials are shown in Table 3.

Table 3. Mechanical properties of materials

Properties	Carbon chromium steel <sup>1</sup>	EN-31 <sup>2</sup>
Hardness ( <i>H</i> ), HRC	61	62
Density ( <i>ρ</i> ), g/cm <sup>3</sup>	7.79	7.81

<sup>1</sup>From laboratory measurements.

<sup>2</sup>From manufacturer.

## 2.3. Tribological testing

By selecting L<sub>9</sub> Taguchi's orthogonal arrays as in Table 2, nine sliding tests were carried out using a ball-on-disc tribometer in accordance with ASTM standard G99-95a [5], as illustrated in Fig. 1. Each test was repeated two times in order to reduce experimental errors. Gas was blown to the sliding surfaces in air at a constant pressure of 10psi (70kPa), as shown in Fig. 2. All tests were performed at room temperature. Prior to the sliding test, both ball and disc were cleaned using acetone in an ultrasonic bath. The ball and disc has a diameter of 11mm and 165mm (thickness of 8mm), respectively.

The frictional force encounters by the ball in sliding were measured by a PC based data logging system. The coefficient of friction (*μ*) is then being determined as follows:

$$\mu = F/W \quad (1)$$

Where *F* is the frictional force in N and *W* is the applied load in N.

Statistical analysis using Taguchi method was then employed to determine the optimal design parameters and investigate the effect of gas lubrication on friction behavior of carbon-chrome steel. Then, a confirmation test was carried out to verify the improvement of the quality characteristic using optimal levels of the design parameters.

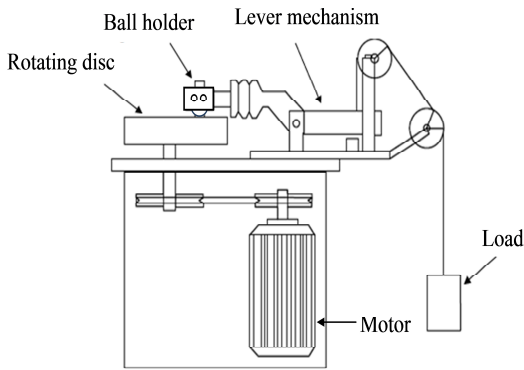


Fig. 1. Schematic diagram of a ball-on-disc tribometer.

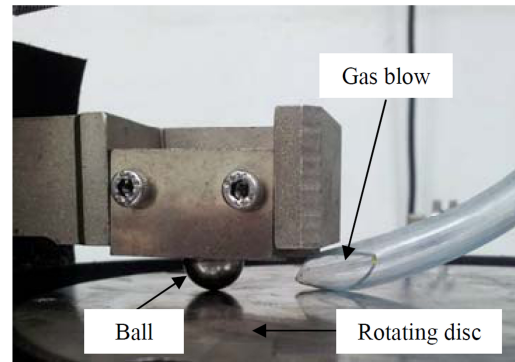


Fig. 2. Photograph of gas blown to the sliding surfaces.

### 3. Results and discussion

#### 3.1 Effect of gas lubrication on friction behavior of bearing material

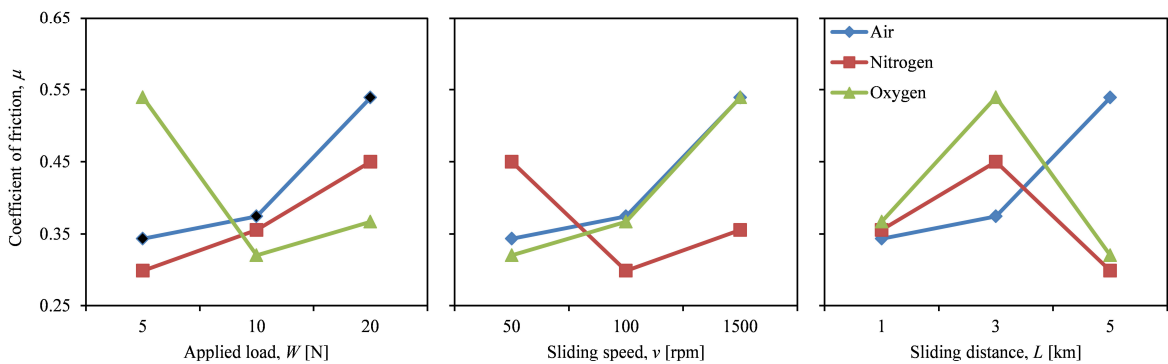


Fig. 3. Interaction plot for coefficient of friction.

Generally, two surfaces of adjacent moving parts can be separated by a thin film to minimize direct contact between them and provides an interface of low shear strength, hence reduce friction and wear. In this study, the presence of gas lubrication potentially created a thin film and lowered the coefficient of friction at higher applied load, sliding speed and sliding distance as compared with the air lubrication, as shown in Fig. 3. This may be due to the shear strength increases less in proportion to the applied load, sliding speed and sliding distance; this leads to a slight reduction of friction.

#### 3.2 Optimal design parameters

In order to quantify the optimal value to each design parameter, mean of *SN* ratio for coefficient of friction was computed, as presented in Fig. 4. A greater *SN* ratio value corresponds to a better performance (low coefficient of friction). A small increase as a mean of *SN* ratio indicating that the presence of  $N_2$ -gas lubrication effectively reduced coefficient of friction. Additionally, based upon the rank of mean of *SN* ratio as shown in Table 4, the sliding speed is the most influencing factors for minimizing coefficient of friction. In this study, the optimal design

parameters for a lower coefficient of friction are identified as follows: lubricant = N<sub>2</sub>, W = 10N, v = 1000rpm, L = 1km.

A comparison between the optimized values in air and N<sub>2</sub>-gas lubrication is shown in Fig. 5. A confirmation test can successfully verify the N<sub>2</sub>-gas lubrication reduced coefficient of friction by 24% (Fig.5(a)). This is in accordance with a significant reduction of wear scar diameter (Fig. 5(b)). Furthermore, Fig. 6 shows that a smoother worn surface (R<sub>a</sub> = 0.162μm) was also obtained under N<sub>2</sub>-gas lubricated conditions.

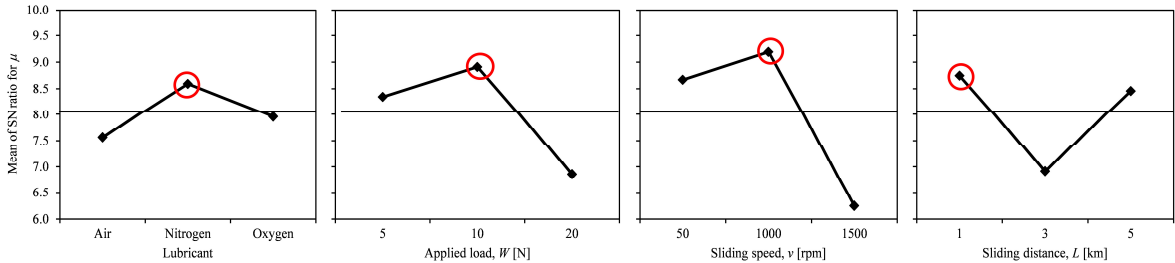


Fig. 4. Mean of SN ratio for coefficient of friction. The optimal design parameters are shown by a red circle.

Table 4. Response table of SN ratios for coefficient of friction

Test	Design parameters			
	Lubricant	Applied load (F), N	Sliding speed (v), rpm	Sliding distance (L), km
1	7.564	8.345	8.667	8.745
2	8.591	8.911	9.193	6.914
3	7.959	6.859	6.254	8.456
Delta	1.027	2.052	2.939	1.831
Rank	4	2	1	3

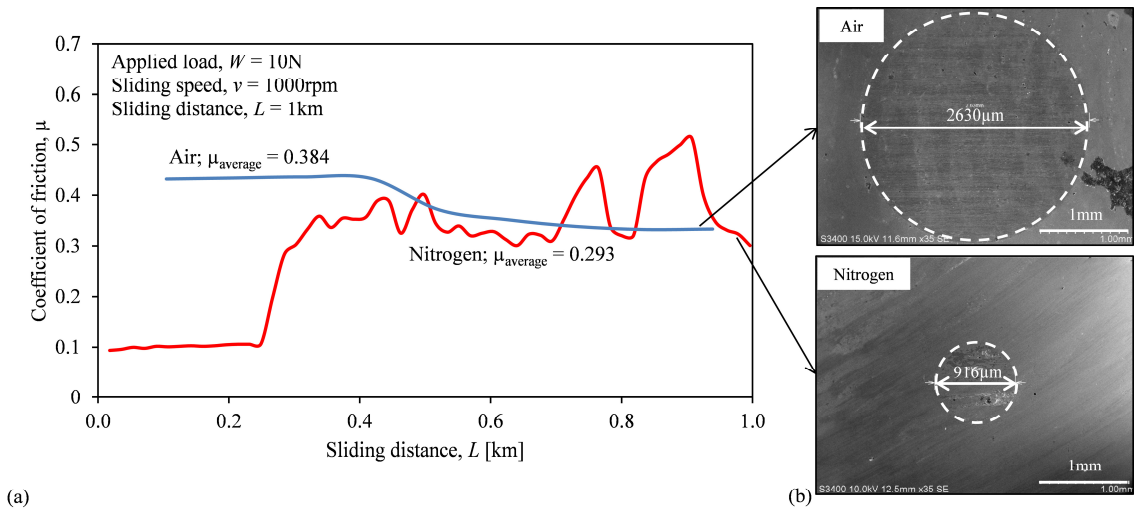


Fig. 5. A confirmation test results by comparing (a) the coefficient of friction and (b) Scanning Electron Microscopy (SEM) of worn surfaces on a ball under air and N<sub>2</sub>-gas lubricated conditions using optimal design parameters.

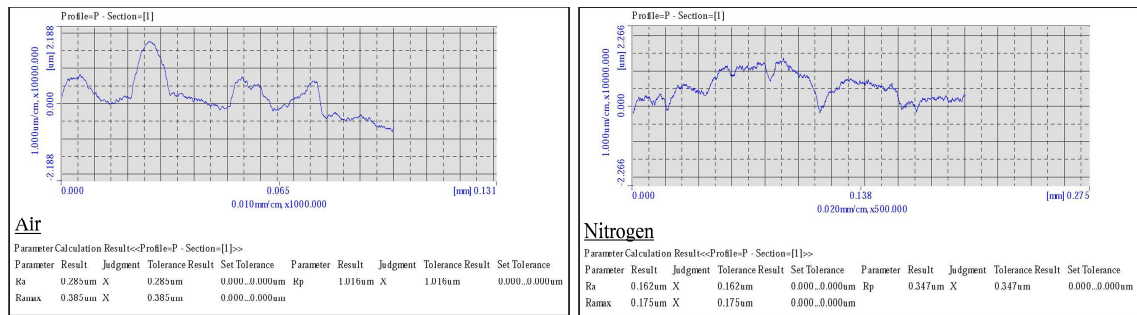


Fig. 6. Surface profile of worn surfaces on a ball under air and N<sub>2</sub>-gas lubricated conditions using optimal design parameters.

#### 4. Conclusions

The following conclusions may be drawn from the present study:

1. As compared to the air lubrication, the presence of gas lubrication lowered the coefficient of friction at higher normal load, sliding speed and sliding distance. This may be due to the shear strength increases less in proportion to the applied load, sliding speed and sliding distance.
2. Based on mean of *SN* ratio analysis, improvement of friction reduction primarily depends on the sliding speed.
3. The optimal design parameters for a lower coefficient of friction ( $\mu$ ) are: lubricant = N<sub>2</sub>,  $W = 10\text{N}$ ,  $v = 1000\text{rpm}$ ,  $L = 1\text{km}$ .
4. By using the optimal design parameters, a confirmation test successfully verified that the N<sub>2</sub>-gas lubrication reduced coefficient of friction by 24%. This is in accordance with a significant reduction of wear scar diameter and smoother worn surface on the ball.

#### Acknowledgements

The authors gratefully acknowledge Prof. Dr. Jaharah Binti A. Ghani for her surface roughness measurement assistance. This research was supported by grant number ERGS/1/2013/TK01/UTEM/02/04, as awarded by Ministry of Higher Education Malaysia (MOHE).

#### References

- [1] Introduction to Air Bearings, Available at [http://www.specialtycomponents.com/intro\\_air\\_bearings.html](http://www.specialtycomponents.com/intro_air_bearings.html), Accessed April 2013.
- [2] Cong, P., Li, T., Mori, S., 2002. Friction-wear behavior and tribochemical reactions of different ceramics in HFC-134a gas, *Wear* 252, p. 662.
- [3] Martin, J.M., Le Mohne, T., Gardos, M., 1990. "Friction of alpha silicon carbide under oxygen partial pressure: high resolution analysis of interface films", *Proceedings of the Conference of ITC, Nagoya, Japan*, pp. 1407–1412.
- [4] Sasaki, S., 1999. Friction and wear behaviour of partially stabilised zirconia in reduced pressure atmospheres containing organic compounds: potential for process lubrication of ceramics, *Lubric. Sci.* 12, p. 67.
- [5] ASTM G99-95a, 2000, Standard Test Method for Wear Testing with a Pin-on-Disk Apparatus, ASTM International, 6 pages.
- [6] Stack, M.M., Mathew, M., 2003. Micro-abrasion transitions of metallic materials, *Wear* 255, p. 14.