



Faculty of Mechanical Engineering

**TRIBOLOGICAL STUDIES OF BIO-LUBRICANT UNDER HIGH
LOADING CAPACITY**

Hayder Saad Oleiwi Al-Nasrawi

**Master of Mechanical Engineering
(Applied Mechanics)**

2016

**TRIBOLOGICAL STUDIES OF BIO-LUBRICANT UNDER HIGH LOADING
CAPACITY**

HAYDER SAAD OLEIWI AL-NASRAWI

**A Dissertation submitted
In fulfillment of the requirements for the degree of Master of Mechanical
Engineering (Applied Mechanics)**

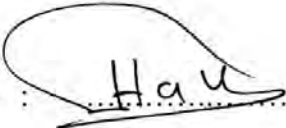
Faculty of Mechanical Engineering

UNIVERSITI TEKNIKAL MALAYSIA MELAKA

2016

DECLARATION

I declare that this dissertation entitled “Tribological studies of bio-lubricant under high loading capacity” is the result of my own research except as cited in the references. The dissertation has not been accepted for any degree and is not concurrently submitted in the candidature of any other degree.

Signature : 

Name : Hayder Saad Oleiwi Al-Nasrawi

Date : 30/9/2016

APPROVAL

I hereby declare that I have read this dissertation and in my opinion this dissertation is sufficient in terms of scope and quality for the award of Master of Mechanical Engineering (Applied Mechanics).

Signature

.....

Supervisor Name

: Dr. Nor Azmmi Bin Masripan

Date

.....*30/9/2016*.....

DR. NOR AZMMI BIN MASRIPAN
KETUA JABATAN (STRUKTUR & BAHAN)
FAKULTI KEJURUTERAAN MEKANIKAL
UNIVERSITI TEKNIKAL MALAYSIA MELAKA

DEDICATION

In the name of Allah, The most Gracious, The most Merciful

All of praise for Allah, glorified and exalted be he. Praise the God for abundant blessings which given to me, and the determination that he gave me to complete this study.

To the great teacher and educator, My Prophet Mohammad (Allah blessings and peace be upon him and his family), which is the light and guidance for the world.

To my lovely parents, the most great and most sacrifice;

To my dear father, who has never spared any effort in our way, I aspire to make him proud of me as much as I am proud of him for his generosity. My beloved mother, which is my gates to paradise, that illuminating with her duaa and love, she removes all my worries by her smiles. Her love and sacrifice cannot be described by words, I did not get to what I am now without their love and sacrifices and their care, and I will not be able to rewarding to them favors in all duration of my live, but I pray for almighty God to protect and save them and bless them paradise.

To my dearest brothers and sisters: Their love, support, duaa and encouragement are meant a lot to me, I ask the God to care and save all for you.

To my lovely wife, dear, and a companion of my life: For her patience and support, and its continuous assist for me. My beloved daughters, they are the privilege of my eyes (Zainab and Ghadeer). I ask and pray to the God to keep and save both of them for me.

For every person who was care of me, even without to be related to me. For your motivation and duaa for me I would like to say: Thank you all.

ABSTRACT

Increased severity in operating conditions coupled with the environmental and toxicity issues related with using conventional lubricants. In addition to, depletion of petroleum reserves and high prices of fossil fuels, have led to exploration of new kind of natural additives as a bio-lubricant. BP as an agricultural wastes are potential to be developed as bio-oils that to replace the petroleum products, due to their environmentally friendly characteristics, being biodegradable, nontoxic and renewable. The purpose of this study are to produce crude oil from BP as a bio additives in paraffin oil, as well as to determine their physical and tribological properties as bio-lubricant under severe operation conditions to identify their ability for lubrication. In this study, ultrasonic homogenizer had been used to mix the lubricants. Brookfield viscometer had been used to determine viscosity of lubricants under various temperatures, while viscosity index had been determined according to ASTM D2270. Tribological performance of BP as a bio-lubricant was tested using a four-ball test machine under extreme pressure conditions, according to ASTM D2783-03. Various lubricating oils (PO and PO+5%, 20%, 50% of banana peel) were tested. The experiments were run for 30 minutes under 500-1750N range of load. The temperatures were set at 27, 80, 100 °C and the sliding speed was set to 1000 RPM. The wear scar and surface roughness were measured using digital microscope and surface roughness tester, respectively. Statistical approach had been used in this the results analyzed was to identify the ability of BP for lubrication. The results focused on density, viscosity, VI, coefficient of friction, wear scar, wear volume losses, Extreme Pressure (EP) Anti-Wear (AW) properties, welding load and surface roughness, which are the basis of comparison between bio-lubricant and paraffin oil. Experimental results showed significant improvement in overall performance with increased BP content compared with paraffin oil through all parameters mentioned above. The results showed that at 100 °C, 50%BP had achieved a highest rate improved compared with paraffin oil in terms of dynamic and kinematic viscosity at rates 250.3% and 229.7% respectively and VI at rate 310.2%. Meanwhile, at 100 °C, lower value of COF at welding point was 0.086 for 50%BP followed by 20%BP, 5%BP and 100%PO at values 0.089, 0.456 and 0.595 respectively. For AW and EP properties, where rates are increase in mean wear scar diameter and welding load at 100 °C of 50%BP compared with paraffin oil was 67.36% and 44.62% respectively. Values of welding loads at 100 °C were 1625 N, 1575 N, 1475 N and 900 N for 50%BP, 20%BP, 5%BP and 100%PO respectively. The results showed that best performance was achieved by mix a 50% of BP in the mineral oil, where COF and WSD could reach their lowest value in extreme operation conditions. As a results, banana peel as EP and AW additives has proven itself able for use in lubrication applications for gears and as engine oils.

ABSTRAK

Peningkatan tahap dalam keadaan operasi yang ditambah pula dengan isu-isu alam sekitar dan ketoksikan yang berkaitan dengan menggunakan pelincir konvensional. Selain, pengurangan rizab petroleum dan harga yang tinggi bahan api fosil, telah membawa kepada penerokaan jenis baru bahan tambahan semulajadi sebagai bio-pelincir. BP sebagai sisa pertanian yang berpotensi untuk dibangunkan sebagai bio-minyak yang untuk menggantikan produk petroleum, kerana ciri-ciri mesra alam mereka, yang mesra alam, tanpa toksik dan boleh diperbaharui. Tujuan kajian ini adalah untuk mengeluarkan minyak mentah dari BP sebagai bahan tambahan bio dalam minyak parafin, dan juga untuk menentukan ciri-ciri fizikal dan tribological mereka sebagai bio-minyak pelincir di bawah keadaan operasi yang teruk untuk mengenal pasti keupayaan mereka untuk pelinciran. Dalam kajian ini, homogenizer ultrasonik telah digunakan untuk campuran pelincir. Brookfield meter kelikatan telah digunakan untuk menentukan kelikatan minyak pelincir di bawah pelbagai suhu, manakala indeks kelikatan telah dipilih mengikut ASTM D2270. prestasi Tribological BP sebagai bio-minyak pelincir telah diuji menggunakan mesin ujian empat bola di bawah keadaan tekanan yang melampau, menurut ASTM D2783-03. Pelbagai minyak pelincir (PO dan PO + 5%, 20%, 50% daripada kulit pisang) telah diuji. Kajian ini telah berjalan selama 30 minit di bawah 500-1750N pelbagai beban. Suhu telah ditetapkan pada 27, 80, 100 ° C dan kelajuan gelongsor ditetapkan kepada 1000 RPM. Memakai parut dan kekasaran permukaan diukur menggunakan digital mikroskop dan permukaan roughness tester, masing-masing. pendekatan statistik telah digunakan dalam hal ini keputusan dianalisis adalah untuk mengenal pasti keupayaan BP untuk pelinciran. Keputusan tertumpu kepada ketumpatan, kelikatan, VI, pekali geseran, memakai parut, memakai kerugian jumlah, tekanan melampau (EP) Anti-Wear (AW) Hartanah, beban kimpalan dan kekasaran permukaan, yang merupakan asas perbandingan antara bio-pelincir dan minyak kuat. Keputusan eksperimen menunjukkan peningkatan yang ketara dalam prestasi keseluruhan dengan peningkatan kandungan BP berbanding dengan minyak kuat melalui semua parameter yang dinyatakan di atas. Hasil kajian menunjukkan bahawa pada 100 ° C, 50% BP telah mencapai kadar yang tertinggi bertambah baik berbanding dengan minyak kuat dari segi kelikatan dinamik dan kinematik pada kadar 250,3% dan 229.7% masing-masing dan VI pada kadar 310,2%. Sementara itu, pada 100 ° C, nilai yang lebih rendah daripada COF pada titik kimpalan adalah 0.086 50% BP diikuti oleh 20% BP, 5% BP dan 100% PO pada nilai 0,089, 0,456 dan 0,595 masing-masing. Bagi hartanah AW dan EP, di mana kadar adalah peningkatan dalam min diameter memakai parut dan beban kimpalan pada 100 ° C 50% BP berbanding dengan minyak kuat adalah masing-masing 67,36% dan 44,62%. Nilai-nilai beban kimpalan pada 100 ° C masing-masing 5% BP dan 100% PO ialah 1625 N, 1575 N, 1475 N dan 900 N 50% BP, 20% BP,. Hasil kajian menunjukkan bahawa prestasi terbaik dicapai dengan campuran 50% daripada BP dalam minyak mineral, di mana COF dan WSD boleh mencapai nilai terendah dalam keadaan operasi yang melampau. Dengan itu, kulit pisang sebagai EP dan bahan tambahan AW telah membuktikan dirinya mampu untuk digunakan dalam aplikasi pelinciran untuk gear dan sebagai minyak enjin.

ACKNOWLEDGMENTS

First my praise is to the Almighty “Allah”, on whom we ultimately depend. Then, I would like to sincerely thank to my supervisor Dr. Nor Azmmi Bin Masripan for his guidance, advices, and support. Without his valuable assistance, this work would not have been completed. My acknowledgment also goes to Universiti Teknikal Malaysia Melaka (UTeM), and especially Faculty of Mechanical Engineering. My acknowledgment also to Mr. Azrul Syafiq Mazlan who is willing to provide an assistance at tribology laboratory. I am also indebted to my friends (Raed Mohammad, Omar Abdul Hasan, Ahmed Ismail, Ahmed Dawood and Amer Adil) for their contributions.

My acknowledgment and thanks for teachers who guarantee me during my study. Most importantly, I am forever grateful my family who understands the importance of this work, none of this would have been possible without their patience and help.

TABLE OF CONTENTS

	PAGE
DECLARATION	
APPROVAL	
DEDICATION	
ABSTRACT	i
ABSTRAK	ii
ACKNOWLEDGMENT	iii
TABLE OF CONTENTS	iv
LIST OF TABLES	vii
LIST OF FIGURES	ix
LIST OF APPENDICES	xiii
LIST OF ABBREVIATIONS	xiv
LIST OF SYMBOLS	xvi
 CHAPTER	
1 INTRODUCTION	1
1.1 Research background	1
1.2 Problem statement	3
1.3 Objective	4
1.4 Scope	5
1.5 Significance of study	6
1.6 Outline of the study	7
 2 LITERATURE REVIEW	8
2.1 Introduction	8
2.2 Regimes of lubrication	9
2.2.1 Boundary lubrication	10
2.2.2 Mixed film lubrication	11
2.2.3 Elastro-Hydrodynamic lubrication	11
2.3 Lubricants	13
2.4 Methods & Devices of tribological tests	15
2.5 Lubricant Additives	18
2.5.1 Types and functional group of lubricant additives	19
2.6 Natural additives in lubrication	21
2.7 Biolubricant	27
2.8 Friction and wear in lubricant additives	32
2.9 Banana peels-based lubricant additives	41
2.9.1 An agriculture & Production & Consumption	41
2.9.2 Composition and anti-oxidation components	44
2.9.3 Applications & Tribological properties	47
2.10 Summary	48
 3 METHODOLOGY	49
3.1 Introduction	49
3.2 Material preparation	51

3.2.1	Banana peel	51
3.2.2	Paraffin oil	51
3.2.3	Ball bearing	52
3.3	Material and methods	53
3.3.1	Lubricant samples	53
3.3.2	Ultrasonic Homogenizer	55
3.3.2.1	Operation conditions	56
3.3.2.2	Spindle of device	57
3.4	Physical properties	57
3.4.1	Measurement of density	57
3.4.2	Measurement of viscosity	58
3.4.3	Description of device Brookfield viscometer model 630D	59
3.4.4	Procedure and the principal of operation	60
3.5	Evaluate of viscosity	61
3.5.1	Evaluate of dynamic viscosity	61
3.5.2	Evaluate of kinematic viscosity	61
3.5.3	Evaluate of viscosity index	61
3.6	Implementation of tribological experiments	62
3.7	Tribological characterization	64
3.7.1	Examination of friction	64
3.7.1.1	Four ball test machine TR-30L	64
3.7.1.2	Description of friction test & Experimental Procedure	66
3.7.1.3	Friction evaluation	68
3.7.2	Wear analysis	68
3.7.2.1	MSP-3080 Digital Microscope	68
3.7.2.2	Description of wear test & Experimental Procedure	70
3.7.2.3	Wear evaluation	70
3.8	Portable surface roughness tester TR200	72
3.9	Summary	72
4	RESULTS AND DISCUSSION	75
4.1	Introduction	75
4.2	Lubricant samples	75
4.3	Physical properties	78
4.3.1	Density of lubricant samples	78
4.3.2	Analysis of Dynamic Viscosity, DV	79
4.3.3	Analysis of Kinematic Viscosity, KV	81
4.3.4	Viscosity index	83
4.4	Tribological characterization	84
4.4.1	Analysis of Coefficient of friction, COF	84
4.4.1.1	Effect of load	84
4.4.1.2	Effect of temperature	89
4.4.1.3	Effect of viscosity (DV and KV)	90
4.4.2	Anti-Wear (AW) and Extreme Pressure (EP) properties	92
4.4.2.1	Effect of load carrying capacity & Weld points	95
4.4.2.2	Effect of temperature	100
4.4.2.3	Dynamic and kinematic viscosity	103
4.4.3	Wear volume losses	106
4.4.3.1	Effect of load on wear volume losses	106
4.4.3.2	Effect of temperature on wear volume losses	109

4.5	Surface Analysis	110
4.5.1	Worn surface characteristics	110
4.5.1.1	Effect of load	110
4.5.1.2	Effect of temperature	113
4.5.2	Surface roughness, Ra (μm)	115
4.5.2.1	Relation between load and surface roughness	115
4.5.2.2	Relation between wear scar and surface roughness	118
4.5.2.3	Volume losses	121
4.6	Summary	122
5	CONCLUSIONS	123
5.1	Conclusion	123
5.2	Recommendations for future research	125
	REFERENCES	126
	APPENDIX A Banana names and synonyms in southeast Asia	139
	APPENDIX B Images some devices used in tribosystem	144
	APPENDIX C Analysis results of viscosity (Dynamic and Kinematic)	146
	APPENDIX D Analysis results of Coefficient Of Friction, COF	147
	APPENDIX E Analysis results of surfaces roughness, Ra (μm)	149

LIST OF TABLES

TABLE	TITLE	PAGE
2.1	Categories of lubricant additives and their functional groups	20
2.2	The concentration range of the main additives in engine oils	25
2.3	Potential applications for various vegetable oils	26
2.4	Bio-degradability of some base fluids	28
2.5	Fatty acid types in structure some of vegetables oils	30
2.6	Kinematic viscosity and viscosity index for different types of vegetable oil	31
2.7	Oil content statistics of some non-edible an edible oil seeds	32
3.1	Mechanical properties of Chrome Alloy Steel Ball bearing	53
3.2	Chemical composition (wt. %) and the hardness of the steel	53
3.3	Composition of lubricant samples	54
3.4	Composition of lubricant samples by using different percentage	55
3.5	Specifications of operation conditions for the LABSONIC P homogenizer model BBI-8535108	56
3.6	Specification of spindle of Ultrasonic Homogenizer device	57
3.7	Laboratory experiments to measure the viscosity (Dynamic and Kinematic) of lubricant samples using Brookfield viscometer model 630D under different temperatures, T (°C)	59
3.8	Specification of viscosity test requirements using Brookfield viscometer model 630D	60
3.9	Implementation of tribological experiments on lubricant samples under three design parameters using four ball test machine TR-30L	63
3.10	General Specifications for using four ball test machine	66

3.11	Specifications of MSP-3080 Digital Microscope	69
3.12	Specifications of portable surface roughness tester TR200	72
3.13	The standards and manual used in this study	73
4.1	Composition of lubricant samples (A, B, C, D) under different percentages	77
4.2	Weld style of metal balls at welding points for lubricant used in this study	86
4.3	Load carrying capacity and WL (Points/Regions) of lubricants at 27 °C	93
4.4	Load carrying capacity and WL (Points/Regions) of lubricants at 80 °C	94
4.5	Load carrying capacity and WL (Points/Regions) of lubricants at 100 °C	95

LIST OF FIGURES

FIGURE	TITLE	PAGE
2.1	Stribeck Curve. Adapted from	9
2.2	Boundary Lubrication. Adapted from	10
2.3	Hydrodynamic Lubrication. Adapted from	11
2.4	Types of commonly known lubricants	14
2.5	Testing methods in tribosystem	17
2.6	World vegetable oil production	22
2.7	Global consumption of vegetable oils by major applications	22
2.8	Vegetable oil production in developing countries	24
2.9	Structures of main saturated and unsaturated fatty acids	29
2.10	Show the following, a) Coefficient of friction at steady state for all type of test lubricants, b) Wear scar diameter on ball bearing lubricated with test lubricants	33
2.11	Wear scar diameter on ball bearing lubricated with test lubricants	34
2.12	Observation of the wear scar condition for RBD palm olein and paraffinic mineral oil	35
2.13	The optical microscope image of (a) coconut oil, (b) sunflower oil, (c) rice bran oil, (d) SAE 20W40	36
2.14	The SEM image of (a) coconut oil, (b) sunflower oil, (c) rice bran oil, (dc) SAE 20W40	37
2.15	COF Vs Temperature, T °C at 1000 RPM	40
2.16	Global banana production	42
3.1	Flow chart shows the methodology of research	50

3.2	Cavendish banana, Musaceae	51
3.3	The following parts show (a) Sound dampening box, Part (b) Photograph of Ultrasonic Homogenizer and instrument used at service, Part (c) Assemble shape of device with accessories	56
3.4	The spindle BBI-853 5140 used in blending the samples	57
3.5	Photograph of Rotational Brookfield viscometer model 630D	58
3.6	Shows the following, (a) Photograph of four ball test machine TR-30L, (b) the schematic diagram of four ball test machine	65
3.7	Shown, a) the 4- Balls – Three in the cup with clamping ring, b) The third in the chuck awaiting location within the spindle, c) Mechanical design of the testing area where the fourth ball inside the spindle	67
3.8	Photograph of MSP-3080 Digital Microscope apparatus	69
3.9	Schematic diagram of wear scar diameter	71
3.10	a) Pick up stylus precision indicator TS110, b) Portable surface roughness tester TR200	73
4.1	Photographs of lubricant samples, a) Banana peel broth before blending, b) PO + 5%BP, c) PO + 20%BP, and d) PO + 50%BP	76
4.2	Lubricant samples versus their weights in (g)	77
4.3	Effect increase of banana peel concentration on density of lubricant	78
4.4	Effect of temperatures, T (°C) on dynamic viscosity, DV (MPa.s)	80
4.5	Effect of temperatures, T (°C) on kinematic viscosity, KV (mm ² / s)	82
4.6	Lubricant samples versus their viscosity index, VI	83
4.7	Effect of Applied load, N on Coefficient of friction, COF at 27 °C	85
4.8	Effect of Applied load, N on Coefficient of friction, COF at 80 °C	87
4.9	Effect of Applied load, N on Coefficient of friction, COF at 100 °C	88
4.10	Effect of temperatures T (°C) on value of coefficient of friction	89
4.11	Effect of dynamic viscosity, MPa.s on Coefficient of friction, COF at welding points	91
4.12	Effect of kinematic viscosity, KV mm ² /s on Coefficient of friction, COF at welding points	92

4.13	Effect of applied load (W in Newton) Versus Minimum Scared Diameter (MSD in mm), for lubricant at 27 °C	96
4.14	Effect of applied load (W in Newton) Versus Minimum Scared Diameter (MSD in mm), for lubricant at 80 °C	98
4.15	Effect of applied load (W in Newton) Versus Minimum Scared Diameter (MSD in mm), for lubricant at 100 °C	99
4.16	Effect BP as additives in AW, EP property and welding point of lubricant under severe operating conditions	99
4.17	Effect of temperature, °C at 700 N on AW and EP properties of test lubricant	101
4.18	Effect of temperature, °C at 1000 N on AW and EP properties of test lubricant	102
4.19	Effect of temperature, °C at WL on AW and EP properties of test lubricant	103
4.20	Effect the viscosity (dynamic and kinematic) of lubricant on produces Wear Scar Diameter (WSD) mm at 27 °C	104
4.21	Effect the viscosity (dynamic and kinematic) of lubricant on produces Wear Scar Diameter (WSD) mm at 80 °C	105
4.22	Effect the viscosity (dynamic and kinematic) of lubricant on produces Wear Scar Diameter (WSD) mm at 100 °C	106
4.23	Effect applied load, N on value of wear volume losses, mm ³ for ball bearings at 27 °C	107
4.24	Effect applied load, N on value of wear volume losses, mm ³ for ball bearings at 80 °C	108
4.25	Effect applied load, N on value of wear volume losses, mm ³ for ball bearings at 100 °C	108
4.26	Effect of temperature on wear volume losses at welding points	110
4.27	Optical micrographs of wear area on the balls surface at 80 °C and the loads 500N, 700N, 1000N and welding points (magnification 200X): (a) Paraffin oil (PO), (b) PO+5%BP, and (c) PO+20%BP	112
4.28	Optical micrographs of wear area on the balls surface at welding points and the 27 °C, 80 °C, and 100 °C (magnification 200X): (a) Paraffin oil (PO), (b) PO+20%BP, (c) PO+50%BP	114

4.29	Surface roughness, Ra (μm) versus load, W (N) at 27 °C	116
4.30	Surface roughness, Ra (μm) versus load, W (N) at 80 °C	117
4.31	Surface roughness, Ra (μm) versus load, W (N) at 100 °C	117
4.32	Surface roughness, Ra (μm) versus Wear scar diameter, WSD (mm) at 27 °C	118
4.33	Surface roughness, Ra (μm) versus Wear scar diameter, WSD (mm) at 80 °C	120
4.34	Surface roughness, Ra (μm) versus Wear scar diameter, WSD (mm) at 100 °C	120
4.35	Surface roughness, Ra (μm) Vs Wear volume losses, mm^3	121

LIST OF APPENDICES

APPENDIX	TITLE	PAGE
A	Images shows popular and unique cultivars of banana in southeast Asia	139
B	Images some devices used in tribosystem	144
C	Analysis results of viscosity, (Dynamic and Kinematic)	146
D	Analysis results of Coefficient Of Friction, COF	147
E	Analysis results of surfaces roughness, Ra (μm)	149

LIST OF ABBREVIATIONS

Abbreviation	Specification
AAA	Authentication, Authorization and Accounting
AO	Antioxidant
AR	Average Readings of three ball
ASE	Automotive Society of Engineers
ASTM	American Society for Testing and Materials
AW	Anti-Wear
BL	Boundary Lubrication
BP	Banana Peel
CEC-L-33-A-94	Coordinating European Council
CMFO	Commercial Metal Forming Oil
COF	Coefficient Of Friction
DV	Dynamic Viscosity
EHL	Elastohydrodynamic Lubrication
EP	Extreme Pressure
F.B.E.P.O.T.M	Four Ball Extreme Pressure Oil Testing Machine
HL	Hydrodynamic Lubrication
HR	Horizontal Reading of three ball
IMSR	Immediate Seizure Region

IP	International Protection Marking
ISR	Initial Seizure Region
JBWR	Just Before Weld Region
KV	Kinematic Viscosity
LaF3-DDP	Lanthanum Trifluoride
LNSR	Last Non Seizure Region
MARDI	Malaysian Agricultural Research and Development Institute
ML	Mixed Lubrication
MWSD	Mean Wear Scar Diameter
PFAD	Palm Fatty Acid Distillate
PO	Paraffin Oil
R&D	Research and Development
RPM	Revolution Per Minute
SBO	Soybean Oil
SKF	Svenska kullagerfabriken
TPC	Total Phenolic Content
VI	Viscosity Index
VR	Vertical Reading of three ball
WL	Weld Load
ZDDP	Zinc dithiodiphosphate

LIST OF SYMBOLS

Symbol	Specification
Ra	Surface roughness
cP	Centipoise
cSt m ² s ⁻¹ (cSt· 106)	Centistoke
C%v/v	Volume/volume percentage
V substance	Volume of substance
V solution	Volume of solution
ρ	Density
ν	Kinematic viscosity
μ	Dynamic viscosity
μ	Coefficient of friction
W	Load
R	Distance
V	Volume losses
d	Wear scar diameter
R	Radius of ball bearing
RPM	Revolution per minute

CHAPTER 1

INTRODUCTION

1.1 Research background

The term “tribology” was derived from the Greek word “τριβος”, which means rubbing or abrasion (Sharma and Mishra, 2015). Tribology can be defined as the science and technology of interacting surfaces in relative motion which are present in various machine elements (Nosonovsky and Bhushan, 2010). In almost every aspect of our daily lives, we meet some appearances of tribology such as sliding, brushing, gripping, holding, machinery works, friction between skin and clothes, movement of artificial hip joints etc (Mattei et al., 2011). Friction is the force resisting the relative motion of solid surfaces, fluid layers and material elements sliding against each other. There are many types of friction like, lubricated friction, fluid friction and dry friction. An important consequence of many types of friction is wear, which may lead to decline in performance and/or damage to components. Wear can be defined as undesired removal of material due to mechanical action (Golshokouh, S. and Ani, 2014). Friction and wear are not material properties but, system properties, depending on the materials used and on the operational (contact) conditions (Cabanettes and Rosén, 2014).

Lubrication is the process or technique employed to reduce friction between two surfaces and wear of one of them or both. As the load increases on the contacting surfaces three clearly positions can be observed with respect to the mode of lubrication, which are called regimes of lubrication.

These regions can be described by the Stribeck curve. Most friction and wear are created during start-up and shutdown of engines, whereas Boundary Lubrication (BL) occurs at low speeds and thin films (Tuszynski, 2006). The major reasons of using lubricants in engines are to control friction properties, reduce wear, enable power generation and to improve the efficiency. Other reasons are for cooling, sealing, load balancing, cleaning and rust prevention. Engine oils consist of the base oil and additives. Mineral based-oil is used in most applications to increase effectiveness in lubrication of various industrial parts fixed and mobile. Although this oil is very useful, it is also an environmental hazard, poses damage on human, has high price and is non-renewable sources (Pettersson et al., 2008; Shi, Huang and Wu, 2015).

In recent years, great development in engines and requirements of the environment is observed. This has led to high efficiency and improvement on load carrying capacity of new and environmentally friendly sources (agricultural waste) especially at severe operating conditions. Vegetable oils as additive have several properties which can achieve this purpose comparable to mineral oils, such as high lubricity, low volatility, high viscosity index, environmental friendly, more biodegradability, low Coefficient Of Friction (COF) and low wear scar (Waara, 2006).

In this study, Banana Peels (BP) had been investigated as an additive in lubrication system. This is a novel attempt to use banana peels (banana skin) in lubrication system. Hence, it is very important and necessary to evaluate the characteristics of BP as a lubricant additive to show their effect on tribological properties at severe condition and to test their validity in industry applications.

1.2 Problem statement

Lubricant oils are one of the main productions from mineral oils as around 90% of lubricant oil derived from mineral oil. Annually more than 35 million tons lubricant oils are used in the world. More than 17 million tons of lubricants are nonrenewable. In addition to, more than 2400 kilo tons of this amount is waste oil; around 72% of waste oil is collected, while more than 674 kilo tons of waste oil uncollected and is enters into environment (Golshokouh et al., 2014). The worldwide governments are concerned over the health-related and environmental effects of petroleum oil, thus requiring environmental laws and need for a highly-efficient, environmentally friendly, biodegradable and renewable lubricants (Lawal, 2013). The molecular structure of vegetable oils has desirable qualities as a lubricant, such as long, polar fatty acid chains which provide high strength lubricant films that interact strongly with metallic surfaces, reducing both friction and wear.

Vegetable oils are particularly effective as boundary lubricants due to high polarity of the entire base components which allows strong interactions with the lubricated surfaces compared with the mineral oil (Ing et al., 2012a; Fox and Stachowiak, 2007). Moreover, in recent days, depletion of non-renewable energy resources, high price and poor performance of conventional mineral-based lubricants have stimulated the use of vegetable oils, especially in severe operating conditions, to be compatible with the great development of engines and requirements of environment. Banana is a tropical fruit grown in over 122 countries worldwide (Ehiowemwenguan et al., 2014). The increasing production of banana has led to increase of agricultural waste generated from its peels (Abbas et al., 2014).

According to scientists, approximately one tons of wastes are produced by every ten tons of bananas (Sharma and Mishra, 2015). To avoid wastage, these banana wastes can be turned into a new energy source (Sharma and Mishra, 2015). There is no study related in tribological properties and ability of banana peel on lubrication in severe loading conditions.